

Rare-earth doped TiO₂ films for the visible light photocatalytic oxidation of ethanol in air.



UNIVERSITEIT
GENT

Iolanda Cimieri¹, Hilde Poelman², Dirk Poelman¹

¹LumiLab, Department of Solid State Sciences, Ghent University, Belgium

²Laboratory for Chemical Technology, Department of Chemical Engineering, Ghent University, Belgium



The photocatalytic activity of TiO₂ as well as its physico-chemical stability, self-cleaning property and high selectivity make it a suitable candidate for the removal of hazardous pollutants such as VOCs from contaminated indoor atmosphere. Since TiO₂ only absorbs light with $\lambda < 380\text{nm}$, most applications are limited to UV light irradiation.

The aim of this study was to extend the spectral sensitivity of TiO₂ to visible light by doping TiO₂ with rare-earth ions, which offer the advantage of transitions in the visible region.

Thin film preparation

The influence of a different number of undoped TiO₂ layers was evaluated upon activity:


Sample	n° layers	Photocatalytic activity $\pm 3\sigma$ (ppm/min)
A	2	3.70 ± 0.10
B	3	3.78 ± 0.06
C	4	3.23 ± 0.13
P25	4	3.44 ± 0.16

Doubly and triply coated undoped TiO₂ films, calcined at 450°C for 2h, are highly active, under UV+visible illumination, if compared with TiO₂ films, prepared by spin coating, from Degussa P25.

A series of 1, 2 and 3wt.% lanthanum, cerium, neodymium, gadolinium, europium, holmium, samarium and dysprosium doped TiO₂ sols were synthesized through a sol-gel method. The films were deposited by spin coating and calcined at 450 °C for 2 hours and compared with undoped TiO₂ films.


Thin film analysis

The microstructure, optical and morphological properties of the films were investigated using XRD, SEM, ellipsometry, XPS, UV/Vis DRS and PL. The triply coated thin films were tested in the breakdown reaction of EtOH as VOC molecule in air under UV and visible light. Photocatalytic measurements were performed in a custom made stainless steel batch reactor, in a controlled Ar/O₂ atmosphere, by means of an atmospheric gas analyser containing a mass spectrometer.

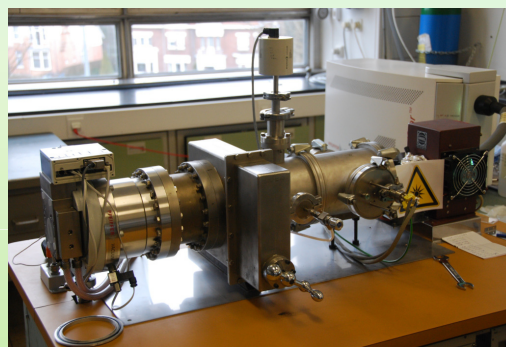


Doping effect

Under UV+vis illumination

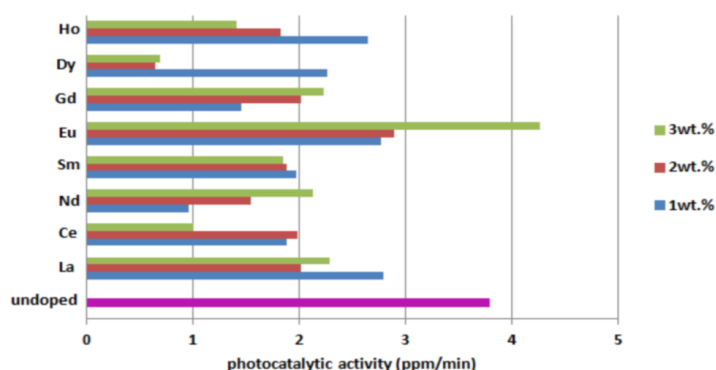

Under visible illumination

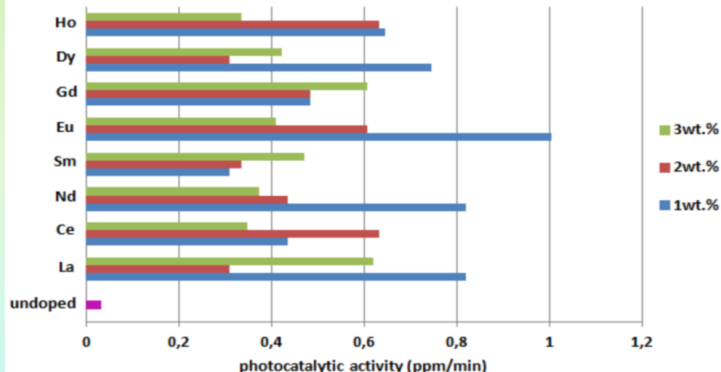

Conclusions

- Undoped sol-gel TiO₂ films of 2 and 3 layers show a higher photocatalytic activity than TiO₂ films prepared from Degussa P25.
- The doping has a great effect on the photocatalytic activity of TiO₂ under visible light.
- The visible response for La, Eu, Nd, Dy and Ho doped TiO₂ is larger for the 1wt.% doped films than for the 2wt.% and 3wt.% ones.
- Among the developed catalysts, the Eu doped titania shows the highest photocatalytic activity under UV+vis (3wt.%) and visible (1wt.%) irradiation.

Acknowledgements

This work was carried out under the Interuniversity Attraction Pole programme IUAP VI/17- INANOMAT funded by the Belgian Science Policy and was also supported by FWO-Flanders.

Contact: iolanda.cimieri@ugent.be